


Standing seam clips

Standing seam clips for nailing or screwing

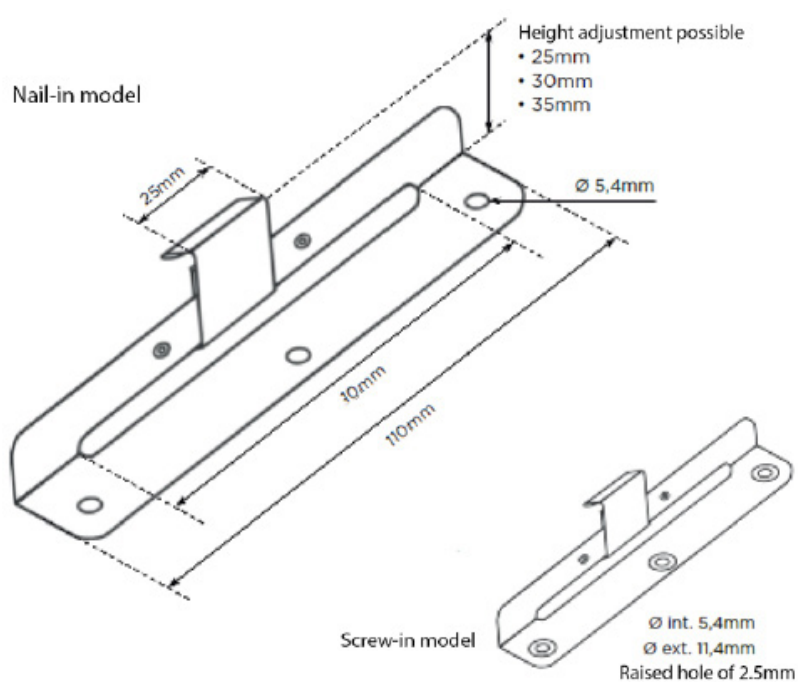


Available materials

Inox 18/10 - Aisi 304
Inox F17 - Aisi 430

Thickness : 0.4mm for the upstand, 0.6mm for the sliding clip

Tensile strength Fmax according to NBN EN ISO 7500-1 : 1605,14 N

Tensile tests

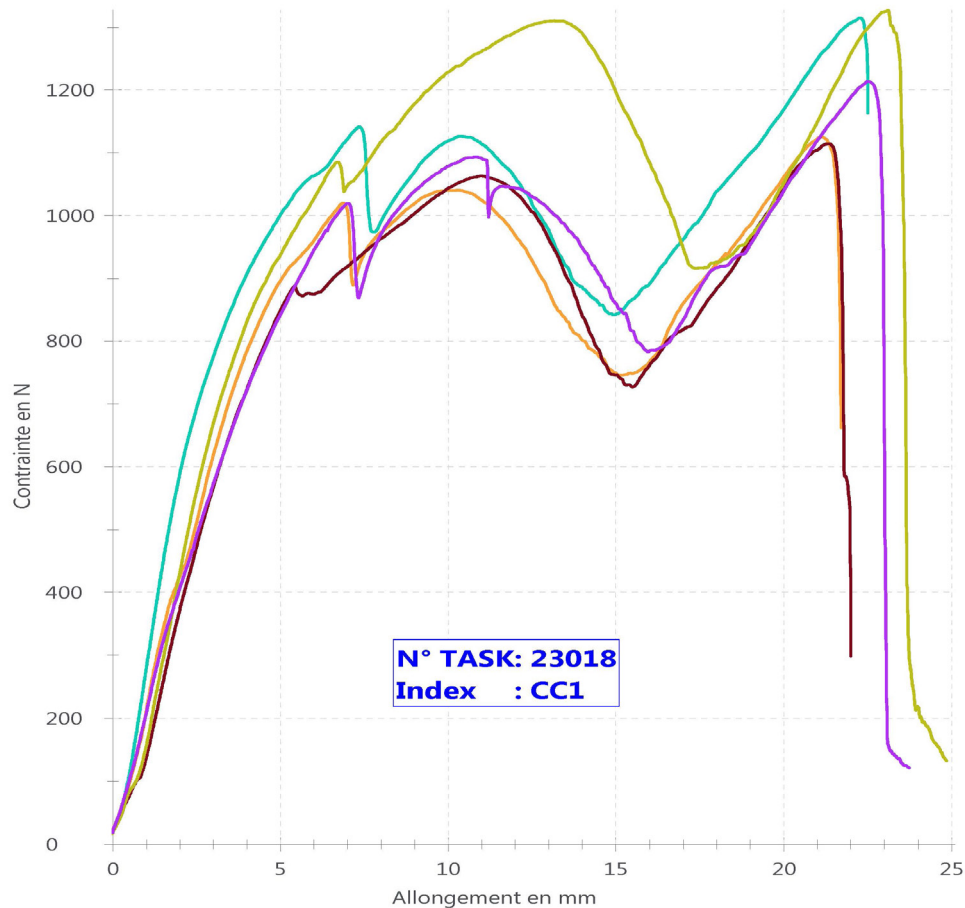

Légende	N°	Index	ID RIMS	F max N	A _{gt} mm	F à rupture N	A _t mm
	28	CC1	32187-1	1125,6	21,2	662,43	21,7
	29	CC2	32187-2	1314,9	22,3	1162,86	22,5
	30	CC3	32187-3	1114,7	21,4	298,95	22,0
	31	CC4	32187-4	1326,7	23,1	132,63	24,9
	32	CC5	32187-5	1213,8	22,5	121,33	23,7

Série	F max N	A _{gt} mm	F à rupture N	A _t mm
n = 5				
x	1219,1	22,1	475,64	23,0
s	100,5	0,8	442,04	1,3
v [%]	8,25	3,66	92,93	5,71

Type et descriptif : Essai de traction
Type d'éprouvette : Pattes métalliques
Température : 20,8 °C
Précharge : 20 N
Vitesse d'essai : 25 mm/min

Demandeur : Fourneaux P.
N° d'étude : RPI2023065_2#1
N° CMD : SCD202500032
N° TASK : 23018
Données machine : Zwick TRA-01
Nom sauvegarde : TRA-TASK23018
Opérateur : Schonmacker P