


CONNECTON
fasteners for builders

Standing seam clips

Standing seam clips for nailing or screwing

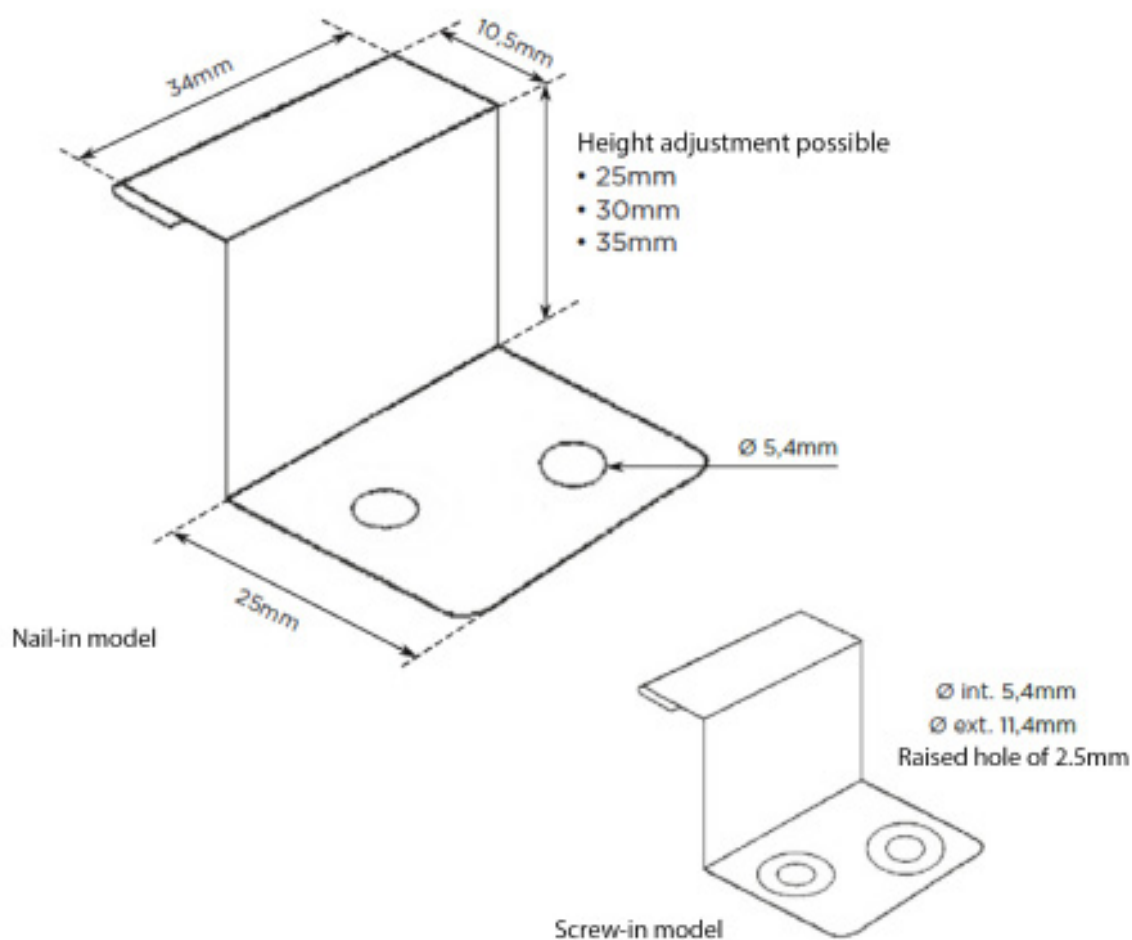


Available materials

Inox 18/10 - Aisi 304

Inox F17 - Aisi 430

Thickness : 0,4mm

Tensile tests

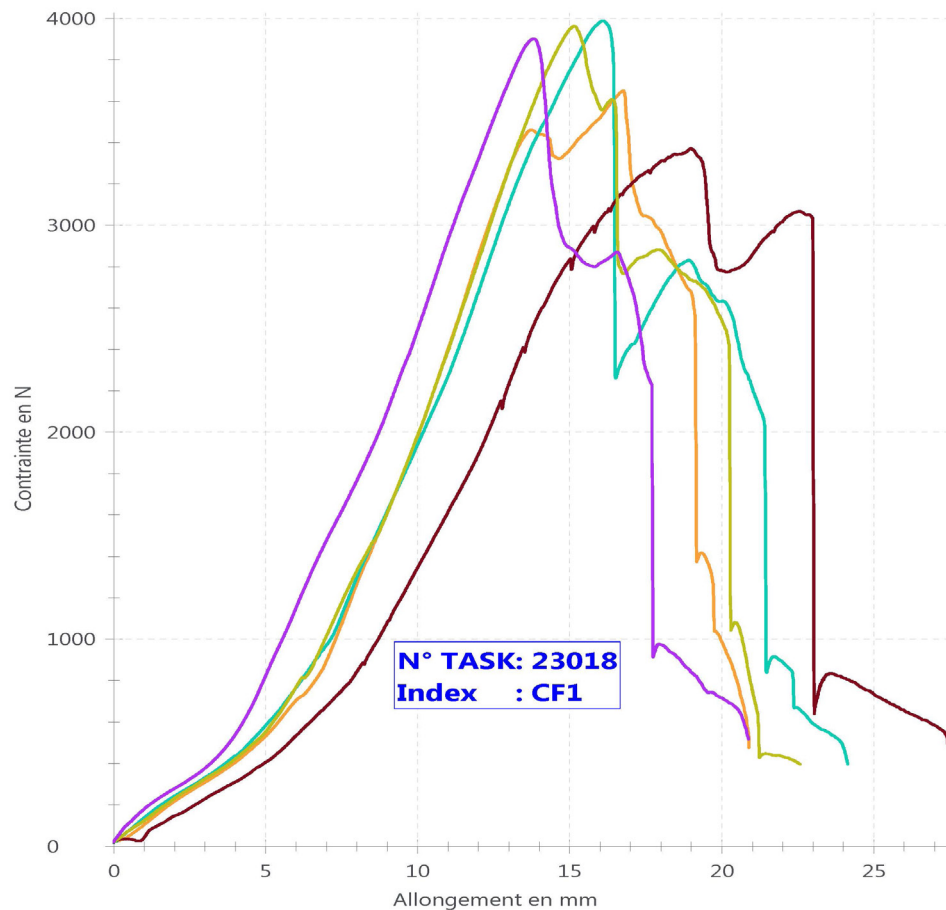

Légende	N°	Index	ID RIMS	F max N	A _{gt} mm	F à rupture N	A _t mm
	8	CF1	32191-1	3651,3	16,8	477,36	20,9
	9	CF2	32191-2	3988,8	16,1	396,75	24,1
	10	CF3	32191-3	3372,6	19,0	493,84	27,4
	11	CF4	32191-4	3962,6	15,1	395,97	22,6
	12	CF5	32191-5	3901,4	13,8	518,27	20,9

Série	F max N	A _{gt} mm	F à rupture N	A _t mm
n = 5				
x	3775,4	16,2	456,44	23,2
s	261,8	1,9	56,74	2,7
v [%]	6,93	11,93	12,43	11,77

Type et descriptif : Essai de traction
Type d'éprouvette : Pattes métalliques
Température : 20,8 °C
Précharge : 20 N
Vitesse d'essai : 25 mm/min

Demandeur : Fourneaux P.
N° d'étude : RPI2023065_2#1
N° CMD : SCD202500032
N° TASK : 23018
Données machine : Zwick TRA-01
Nom sauvegarde : TRA-TASK23018
Opérateur : Schonmacker P